

FACTORS THAT INFLUENCE THE STEEL HARDENING PROCESS

Pavel MUDURA

University of Oradea, pmudura@uoradea.ro

Keywords: Steel quenching, quench capacity; hardenability;

Abstract: This paper is an analysis of the factors that influence the processes taking place in martensitic hardening of steels and the results of hardening. Thus, the main features highlighted are: strengthen steels, liquid cooling that occurs during hardening.

1. INTRODUCTION

In the current technologies for processing of metallic materials, heat treatments have an important place, being responsible for both technological properties and final properties of the part that is produced from the material. One of the most important is the hardening heat treatment. Over time, a large number of steels have been and diversified hardening processes appeared which, can produce high hardness and tensile strength and at the same time, as low as possible internal tensions.

Next, we will refer only to martensitic type hardening of steels, which mainly consists of: obtaining austenitic structure by heating, followed by a rapid cooling in order to obtain the martensitic structure.

2. CHARACTERISTICS OF STRENGTHENED STEELS

2.1 Basic characteristics

These characteristics are determined by the steel making process and by operations suffered during the quenching process. These are

a) *Chemical composition*, which influences decisively: the thermophysical parameters and the quenching capacity of steel. All alloying elements excepting the cobalt, decreases the thermal conductivity of the steel which includes it.

b) *Thermal effusivity* of steel and of the cooling medium. Thermal effusivity is a quantity that influences the temperature of initial contact [2], which is established in the first instant of contact of a body of temperature T_1 and effusivity E_1 , with a cooling media of average temperature T_2 and effusivity E_2 :

$$T_{ci} = \frac{T_1 \cdot E_1 + T_2 \cdot E_2}{E_1 + E_2} \quad (1.1)$$

where T_{ci} is the initial contact temperature, in ° C

c) *The initial structure of steel*, which is determined by the thermal history of the part and the way the part was processed (casting, forming, etc.).

d) *The form and dimensions of the part*, determines the distribution of mass in space and therefore will determine the thermal gradient section of the part, during cooling, affecting quench results. In the same time this parameter has direct influence on the size of internal tensions.

e) *The state of part surfaces*, refers to the size or roughness of the surface or its chemical nature (oxides, and so on) and has a direct influence on heat exchange, part-coolant. Roughness in general has little influence on the rate of cooling, but high roughness increases the cooling speed. As far as surface oxides are concerned, to a certain thickness (hundredths of mm) lead to the growth in cooling rate, and over this thickness leads to lower cooling rate [2].

2.2 Technology parameters of quenching

Austeniting (heating) parameters. Austenitic structure obtained by heating is characterized mainly by the austenite grain size and degree of homogenization. These quantities, which have a decisive influence on the mechanical properties after quenching, are determined by the following parameters: temperature and duration of austeniting.

a) *Austeniting temperature* is chosen so as to obtain a homogeneous austenite and fine grain size. A too high austeniting temperature favors coarse grain leading to a rough martensite which is harder but fragile.

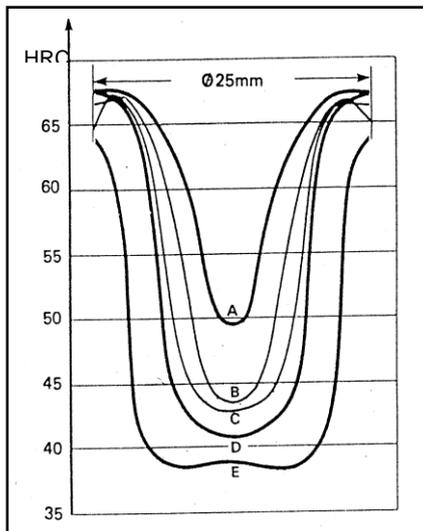


Figure 1. Influence of grain size of austenite on the hardness of steel with 0.75% C; 0.75% C, A- large grains E - average grains [3].

b) *The duration austeniting* is responsible for completion of structural transformations, austenite homogenization and of austenite grain growth which has as result, on one hand, increased hardness and hardening depth, (Figure 1), and on the other hand, the increasing fragility of tempered steel and thus, the risk of cracking. As a result, this increase is not recommended in practice for increasing of hardenability.

Cooling parameters. The cooling of austenite, in order to transform it into martensite or bainite is done using certain cooling medium at a temperature lower than the austeniting temperature. These cooling media can be: liquids, gases, solids or mixed.

Cooling of a austenited parts using a cooling liquid, is the evolution of temperature field in the part's volume during cooling. Heat exchange between part and a certain cooling liquid, can be influenced by modifying the following parameters:

- a) initial temperature of the part;
- b) cooling liquid temperature;
- c) part-liquid relative speed (shaking);
- d) concentration of the liquid - for liquid solutions.

These are the main technological parameters by which we can influence to some extent, the evolution of temperature field in the volume part and therefore the results of quenching part.

2.3 Final Features

Quenching is a heat treatment technology which has an important impact on most metal products, due to mechanical properties that are provided to them. So a heat treatment cycle specific to hardening, applied to a steel, together with structural changes and internal tensions, produces the following main effects [12, 13]:

a) **Modification of mechanical properties.** The bainitic or martensitic structure, resulting from hardening of steel, results on one hand, in increased hardness, elastic limit, tensile strength, fatigue resistance and wear resistance, and on the other hand, a decreased resilience, elongation at break and tensile shrinking.

b) **Changing of dimensions.** This is due to the difference between specific volumes of the structural constituents before and after quenching, and of internal tensions. These dimensional changes depend on a number of factors: the type of steel, hardening parameters, form and product dimensions, and so on.

c) **Forming of internal tensions.** Quenching of a part, implies the existence of cooling operation which has an evolutionary nature from the outside inwards and is accompanied by phenomena of contraction and phase transformation with changes in specific volumes. These phenomena produces internal tensions in the part, which are currently classified as: *heat stress* - caused by non simultaneous contractions of the parts sections, *structural stress* - caused both by differences in specific volumes of existing and newly formed phases and the non simultaneous occurrence of new phases in the part's section; *tensions of the crystal lattice*, which are produced in each grain, being specific for equilibrium phases obtained by a martensitic type transformation. The last of these tensions are reflected in the hardness of the phase and therefore they can be useful in certain circumstances. All these internal tensions overlap, so that the resultant tensions can lead to elastic deformation, plastic deformation or even local cracking of part material.

Some of these deformations, which remain present in the part after quenching, in turn may generate new internal tensions. These tensions, together with the structural tensions of the crystal lattice, which also are present after quenching, form the so-called residual tension.

In conclusion, at the part level, thermal stresses and structural tensions can manifest themselves through structural deformation or cracking of the part and therefore should be reduced as much as possible, and the tensions of the crystal lattice is manifested by increasing hardness, so conditions will be created for these to show up in desired parts of the work piece.

Factors that influence and determine the quenching process are presented in Table1.

Technological characteristics of a steel in relation to its ability to cool, are:

- *hardening capacity*, which is the maximum hardness that can be achieved by hardening steel (it's martensite hardness);

- *hardenability*, which is the ability to harden steel for a certain depth.

Table 1. - Factors influencing steel quench process

a) factors preceding cooling	Type of steel	- chemical composition, homogeneity - peculiarities of development		
		- Structural condition	- thermal history of the structure - grain size	
		- state of internal tension		
		- thermophysics factors and state parameters	- thermal conductivity - specific heat - expansion coefficient - density	
	Work piece	- form of the piece - the part dimensions - The ratio surface / volume [m ⁻¹]		
		- particularities technological	- plastic deformation, casting, etc.	
		- state surfaces	- roughness - chemical nature	
		- austenitizare conditions	- temperature - period	
	cooling liquid	-nature of the liquid		
		- physical properties and state parameters	- viscosity - surface tension - temperature - pressure - density - volume	
		- chemical properties	- concentration - molecular weight - chemical stability	
		- hydrodynamic factors	- free convection - forced convection (degree of agitation) - Laminar flow - turbulent flow - transitional regime	
		- thermophysical factors	- temperature vaporization - saturation temperature - latent heat of vaporization - specific heat - thermal conductivity	
	b) factors during cooling	interaction part-liquid	- Cooling method (immersion, spraying. etc.) - reactivity to the part - piece-liquid temperature difference - behavior of fluid motion relative to the track - wetting characteristics - the relative speed-piece liquid cooling (shaking) - effective heat transfer coefficient - rate of heat stored in the part / volume of liquid - izofilm phenomenon: a thin surface deposit piece - structural changes - intensity of physical fields (gravitational, electrostatic, ultrasonic, etc.).	
	c) post-cooling factors	- after cooling temperature - structure after cooling;		

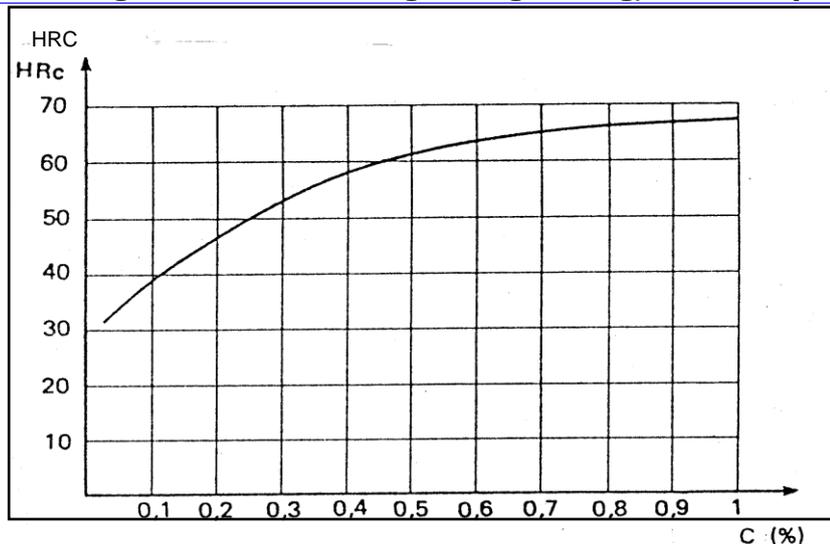


Figure 2. Influence of carbon on the hardness of martensite [3]

Hardening of steel capacity is essentially influenced by the percentage of carbon, as shown in Figure 2. Hardenability of carbon steel is relatively small and it increases particularly as function of the alloy elements [3].

Effects of hardening of a part can be controlled to some extent by either changing some parameters of technological processes, or by the quenching process itself (austeniting and cooling of the part). As a result, these technological parameters can be grouped as follows:

- Initial: type and condition of structural steel;
- of austeniting: temperature and duration of austeniting;
- of cooling: the type and temperature of the coolant, liquid-part relative velocity.

3 CONCLUSIONS

Following the analysis of a rich literature, the following conclusions:

- hardening by quenching of steel parts, occurs as a result of a complex transformation process that is influenced by several factors (Table 1). Main hardening occurs during cooling of austenite, which is determined both by the cooled part and also by the environment which makes the cooling. As a result, that hardening by quenching is a property of the couple: part - cooling medium.

- results of the hardening of a specific steel, are usually measured by the amount of martensite formed respectively by varying the depth of hardening.

- providing more accurate results of a specific hardening steel, requires an accurate knowledge of thermophysical properties of steels and cooling liquids, and the parameters occurring in the process.

4. Bibliografie

1. *** Metals Handbook, vol. 4 (Heat Treating), American Society for Metals 1991, 68-120
2. MUNTEANU, AL., Contribuții la studiul teoretic și experimental al transferului de căldură... (teză de doctorat), Universitatea din Brașov, 1978.
3. MANSION, J., BOURNICON, C., SAYETAT, C., Les Huiles de Trempe - Edition CETIM – 1978.
4. TENSI, H., M., STICH, A., Fundamentals About Quenching by Submerging, în : "International Heat Treating Conference : Equipment and Processes", ASM International, Materials Park, Ohio, 1994.
5. TOTTEN, G., Principles and Applications of the Immersion, în : "International Heat Treating Conference : Equipment and Processes", ASM International, Materials Park, Ohio, 1994.
6. Ma S., Aparna, S., Varde, S., Takahachi, M., Rondeau, D.K., Maniruzzaman, M., Sisson, R.D., in: Proceedings of 4th International Conference on Quenching and Control of Distortion, Beijing, 20–23 May 2003.
7. Toten, G.E., Canale, L.C.F., Agnelli, R., Sarmiento, G.S., Riofano, R.M.M., Bugna, J.F., Project: Villares Quench System Development, Part IV, 2006.
8. Kuyucak, S., Newcombe, P., Bruno, P., Grozdanich, R., Looney, G., Heat Treating Process (January/February) (2005) 60–63.
9. Kuyucak, S., Newcombe, P., Bruno, P., Grozdanich, R., Looney, G., Heat Treating Process (March/April) (2005) 42–44.
10. Totten, G.E., Bates, C.E., and N.A. Clinton: Handbook of Quenching and Quenching Technology, ASM International, Materials Park, OH, 1993, pp. 1-160.
11. Tszeng, C., and Nash, P.: "Modelling Heat Treating Processes," Indust. Heating, 2001, 68, pp. 12-14.
12. Bates, C.E., Totten, G.E., and Orszak, K.B.: "Quench Severity Effects on the Properties of Selected Steel Alloys" in Proc. 3rd Seminar of the International Federation for Heat Treatment and Surface Engineering, The Institute of Materials, London, UK, pp. 55-69.
13. Bates, C.E., and Totten, G.E.: "Estimating Quench Severity With Cooling Curves I," Indust. Heating, 1992, 59, pp. 24-26.
14. Kobasko, N.I., Moskalenko, A.A., Totten, G.E., and Webster, G.M.: "Experimental Determination of the First and Second Critical Heat Flux Densities and Quench Process Characterization," J. Mater. Eng. Performance, 1997, 6, pp. 93-101.
15. Narazaki, M., Kogawara, M., Shirayori, A., and Fuchizawa, S.: "Accuracy of Evaluation Methods for Heat Transfer Coefficients in Quenching" in Proc. 18th Conference of Heat Treating Symposium Including the Lui Dai Memorial Symposium, ASM International, Materials Park, OH, 1998, pp. 509-17.
16. Geiger, G.H., and Poirier, D.R.: Transport Phenomena in Materials Processing, Minerals, Metals & Materials Society, Warrendale, PA, 1994, p. 17.